



Novel methodology based on green chemistry for obtaining extracts rich in polyphenols from upcycled cork by-product

Bermúdez, Manuela¹; González-Trejo, Ana²; Verdum, Maria³; Jové, Patricia³; Pomares, Laura¹; Godoy-Cancho, Belén²

¹ R&D QUIMIVITA SA, Barcelona, Spain;
² Instituto del Corcho, la Madera y el Carbón Vegetal (ICMC)/Centro de Investigaciones Científicas y Tecnológicas de Extremadura (CICYTEX), Junta de Extremadura, Mérida, Spain;
³ R&D, Institut Català del Suro, Palafrugell, Spain.

POSTER ID4386

Introduction

Cork is the bark of the cork oak (*Quercus suber* L.), a perennial tree species native and exclusive to Mediterranean forests. The production of cork is possible thanks to the capacity of the cork oak to generate suberous tissue continuously throughout its life.

Cork is a natural material of great value but its industry involves an environmental problem, such as the pollutant load of cork boiling waters [1,2] and the generation of solid waste from the different operations of the industry [1]. However, there is the paradox, that these wastes contain compounds have excellent properties as natural antioxidants and anticarcinogens and, therefore, with applications in the pharmaceutical, cosmetic and food industry [3].

The chemical composition of cork is substantially different from other parts of the tree since cork has some "free" components, not chemically linked to the main structure and, therefore, extractable with solvents [4,5]. One of the most important extractable compounds are phenolic compounds, which are extracted with polar solvents, such as water or methanol, as well as compounds such as phenolic acids, phenolic aldehydes, and coumarins, also include compounds belonging to the chemical families of flavonoids and tannins [3,4].

Phenolic compounds are substances of great interest due to their biological properties, such as antioxidant, antithrombotic, antibacterial, antiallergic, anticancer and anti-inflammatory activity [3,6-8]. Thanks to these properties, they are considered part of the so-called bioactive compounds, i.e., compounds that have a beneficial influence on cellular activity and therefore on health [9]. The interest in natural phenolic compounds have increased considerably in recent years, in addition to their properties, for not presenting adverse effects as often occurs with their synthetic counterparts [10].

Materials & Methods

Raw materials and sample preparation

The cork industry by-products studied were cork boiling water and solid cork residues: 0.5-2.0 mm granulated, high density granulated and cork back (ADT), high density granulated (AD) and mill cork dust (PR).

Samples characterization

- Total phenolic contents (TPC)
- Antioxidant activity (AA) and the half maximal inhibitory concentration (IC50).
- Low molecular weight phenolic compounds.

Phenolic extractions

- **Solid phase extraction for cork boiling waters**
 - The samples of cork boiling water were pre-treated to preconcentrate the phenolic compounds and eliminate interfering compounds. This pre-treatment was performed by solid phase extraction (SPE) with HyperSep C18 cartridges (200mg/3 mL).
- **Traditional methods:** suspension, sonication, Soxhlet.
- **Optimization of extraction processes based on green chemistry:** sonication, maceration, Microwave assisted extraction (MAE), Accelerated solvent extraction (ASE).

Conclusions

The methodology developed in our study follows the guidelines of green chemistry. The cork extracts obtained were rich in phenol compounds with good antioxidant activity. These results, together with the phenolic content values, demonstrate the usage of green chemistry methodology to obtain a cork extract and confirm the potential of these residues as a source of high value compounds.

Acknowledgements

This research has been carried out within the framework of the CORK2WINE project (IDI-20200659, CIEN Strategic Program), with the financial support of the CDTI and the European Union, through the European Regional Development Fund (ERDF). Ana González Trejo thanks the ESF for the funding received under the Youth Employment Operational Program 2014-2020.

References

- Sepúlveda FJ (2014) Aprovechamiento selectivo para la valorización integral de residuos de la industria del corcho. Doctoral Thesis. University of Extremadura.
- Ponce-Robles L (2018) Tratamiento de aguas residuales mediante procesos basados en la radiación solar y el ozono. Evaluación mediante técnicas analíticas y microbiológicas avanzadas. Doctoral Thesis. University of Almería.
- Godoy-Cancho B (2017) Composición bioactiva de materiales lignocelulósicos. Determinación de compuestos fenólicos y elagitaninos con propiedades antioxidantes y anticancerígenas mediante técnicas analíticas diversas. Doctoral Thesis. University of Extremadura.
- Silva SP, Sabino MA, Fernandes EM, et al (2013) Cork: properties, capabilities and applications. *International Materials Reviews*, 50, 6:345-365.
- Pereira H (2007) The chemical composition of cork. *Cork: Biology, production and uses*. Elsevier 55-99.
- Santos SAO, Villaverde JJ, Sousa AF, et al (2013) Phenolic composition and antioxidant activity of industrial cork by-products. *Industrial Crops and Products* 47:282-289.
- Bejarano I, Godoy-Cancho B, Franco L, et al (2015) *Quercus Suber* L. Cork extracts induce apoptosis in human myeloid leukaemia HL-60 cells. *Phytotherapy Research* 29:1180-1187.
- Cariño C, Ribeiro HM, Marto J (2018) Converting cork by-products to ecofriendly cork bioactive ingredients: Novel pharmaceutical and cosmetics applications. *Ind. Crops. Prod.* 125:72-84.
- Bouras M, Chadni M, Barba FJ, et al (2015) Optimization of microwave-assisted extraction of polyphenols from *Quercus* bark. *Industrial Crops and Products*, 77:590-601.
- Santos SAO, Pinto PCRO, Silvestre AJD, Neto CP (2010) Chemical composition and antioxidant activity of phenolic extracts of cork from *Quercus suber* L. *Industrial Crops and Products* 31(3): 521-526.
- Singleton VL, Rossi JA (1965) Colorimetry of total phenolics with phosphomolybdic-phosphotungstic acid reagents. *Amer. J. Enol.Viticult.* 16: 144-58.
- Thaipong K, Boonprakob U, Crosby K, et al (2006) Comparison of ABTS, DPPH, FRAP, and ORAC assays for estimating antioxidant activity from guava fruit extracts. *Journal of Food Composition and Analysis* 19(6-7): 669-675.
- Rodríguez-Romero M, Godoy-Cancho B, Calha I, et al (2021) Allelopathic Effects of Three Herb Species on *Phytophthora cinnamomi*, a Pathogen Causing Severe Oak Decline in Mediterranean Wood Pastures. *Forests* 12(3):285.
- Sousa AF, Pinto PCRO, Silvestre AJD, Neto CP (2006). Triterpenic and other lipophilic components from industrial cork by-products. *Journal of Agricultural and Food Chemistry* 54(18):6888-6893.
- Fernandes A, Sousa A, Mateus N, et al (2011) Analysis of phenolic compounds in cork from *Quercus suber* L. *Journal of Agricultural and Food Chemistry* 59(14):7414-7420.
- Herrero M, Martín-Alvarez PJ, Senorans FJ, et al (2005) Optimization of accelerated solvent extraction of polyphenols from *Quercus suber* L. bark. *Food Chemistry* 93(2):417-424.

Results & Discussion

Cork boiling water: In the direct analysis of the ten cork boiling water samples values of 1101 mg gallic acid equivalents (GAE)-L-1 for total phenolic content, 0.52 mmol Trolox-L-1 for antioxidant activity were obtained and eight low molecular weight phenolic compounds were identified. For the cork boiling water pretreated, the increase of phenolic compounds is approximately of 56%.

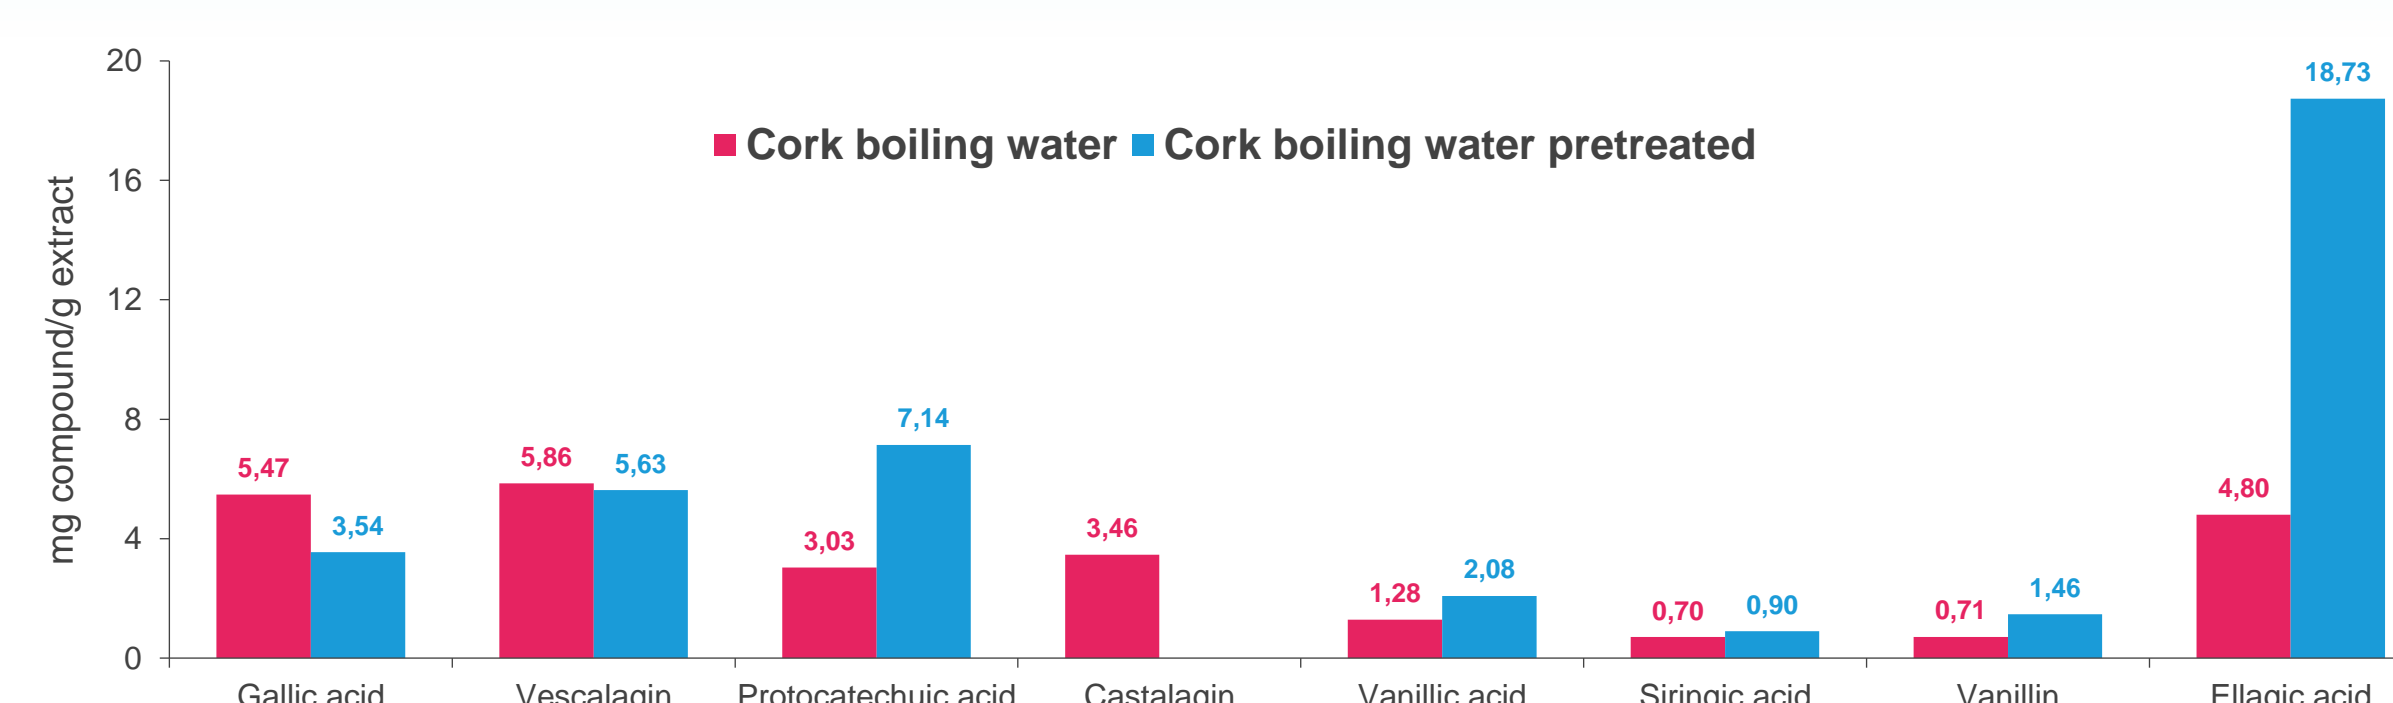


Figure 1. Comparison of low molecular weight phenolic compounds of cork boiling water and the same water pretreated by SPE.

Solid cork residues: Traditional methods

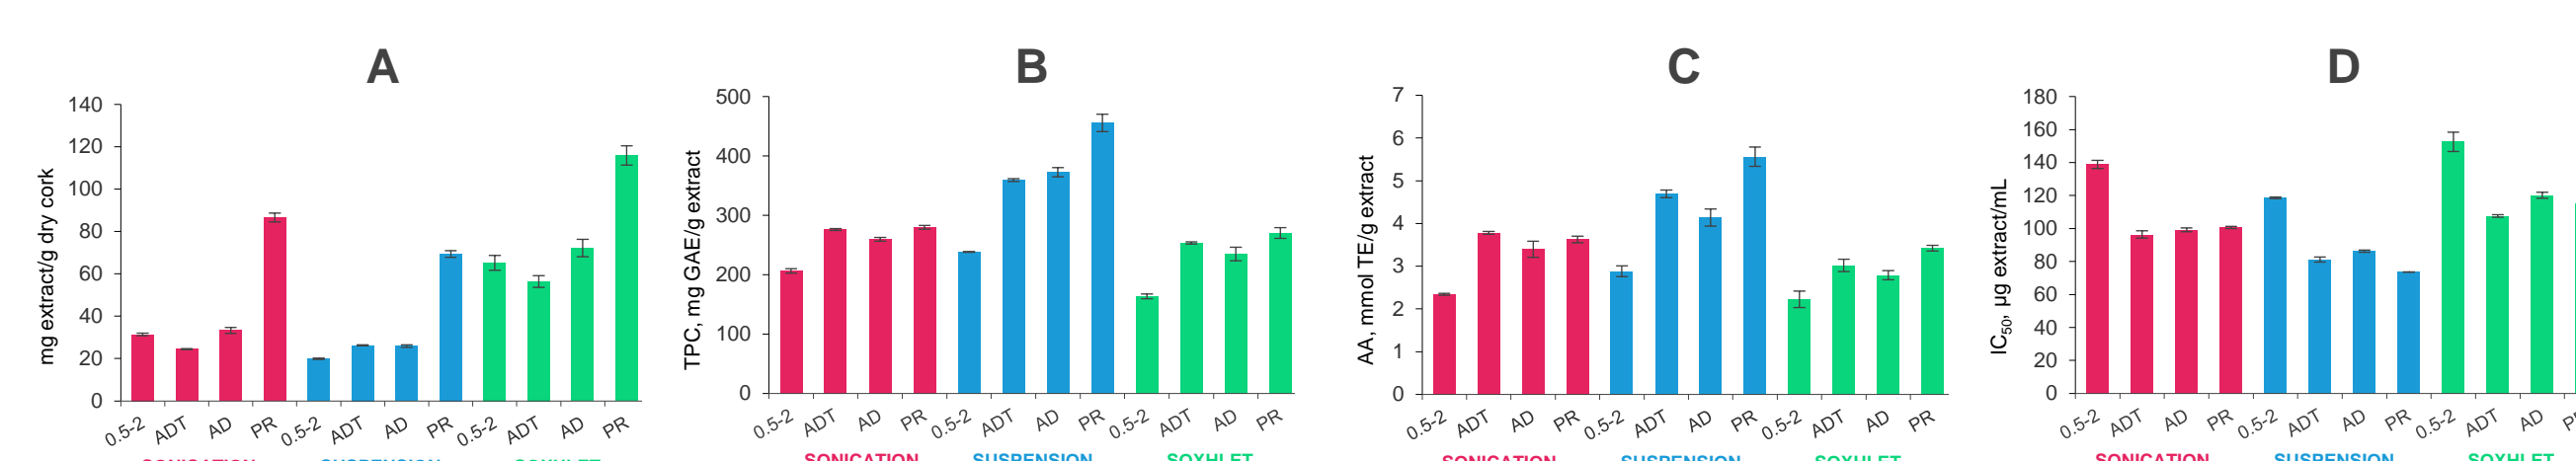


Figure 2. Characterization of extracts obtained by traditional methods: sonication (pink), suspension (blue) and soxhlet (green). A: Yield of the extraction process; B: Total phenolic content; C: Antioxidant activity; D: IC50.

Solid cork residues: Green chemistry

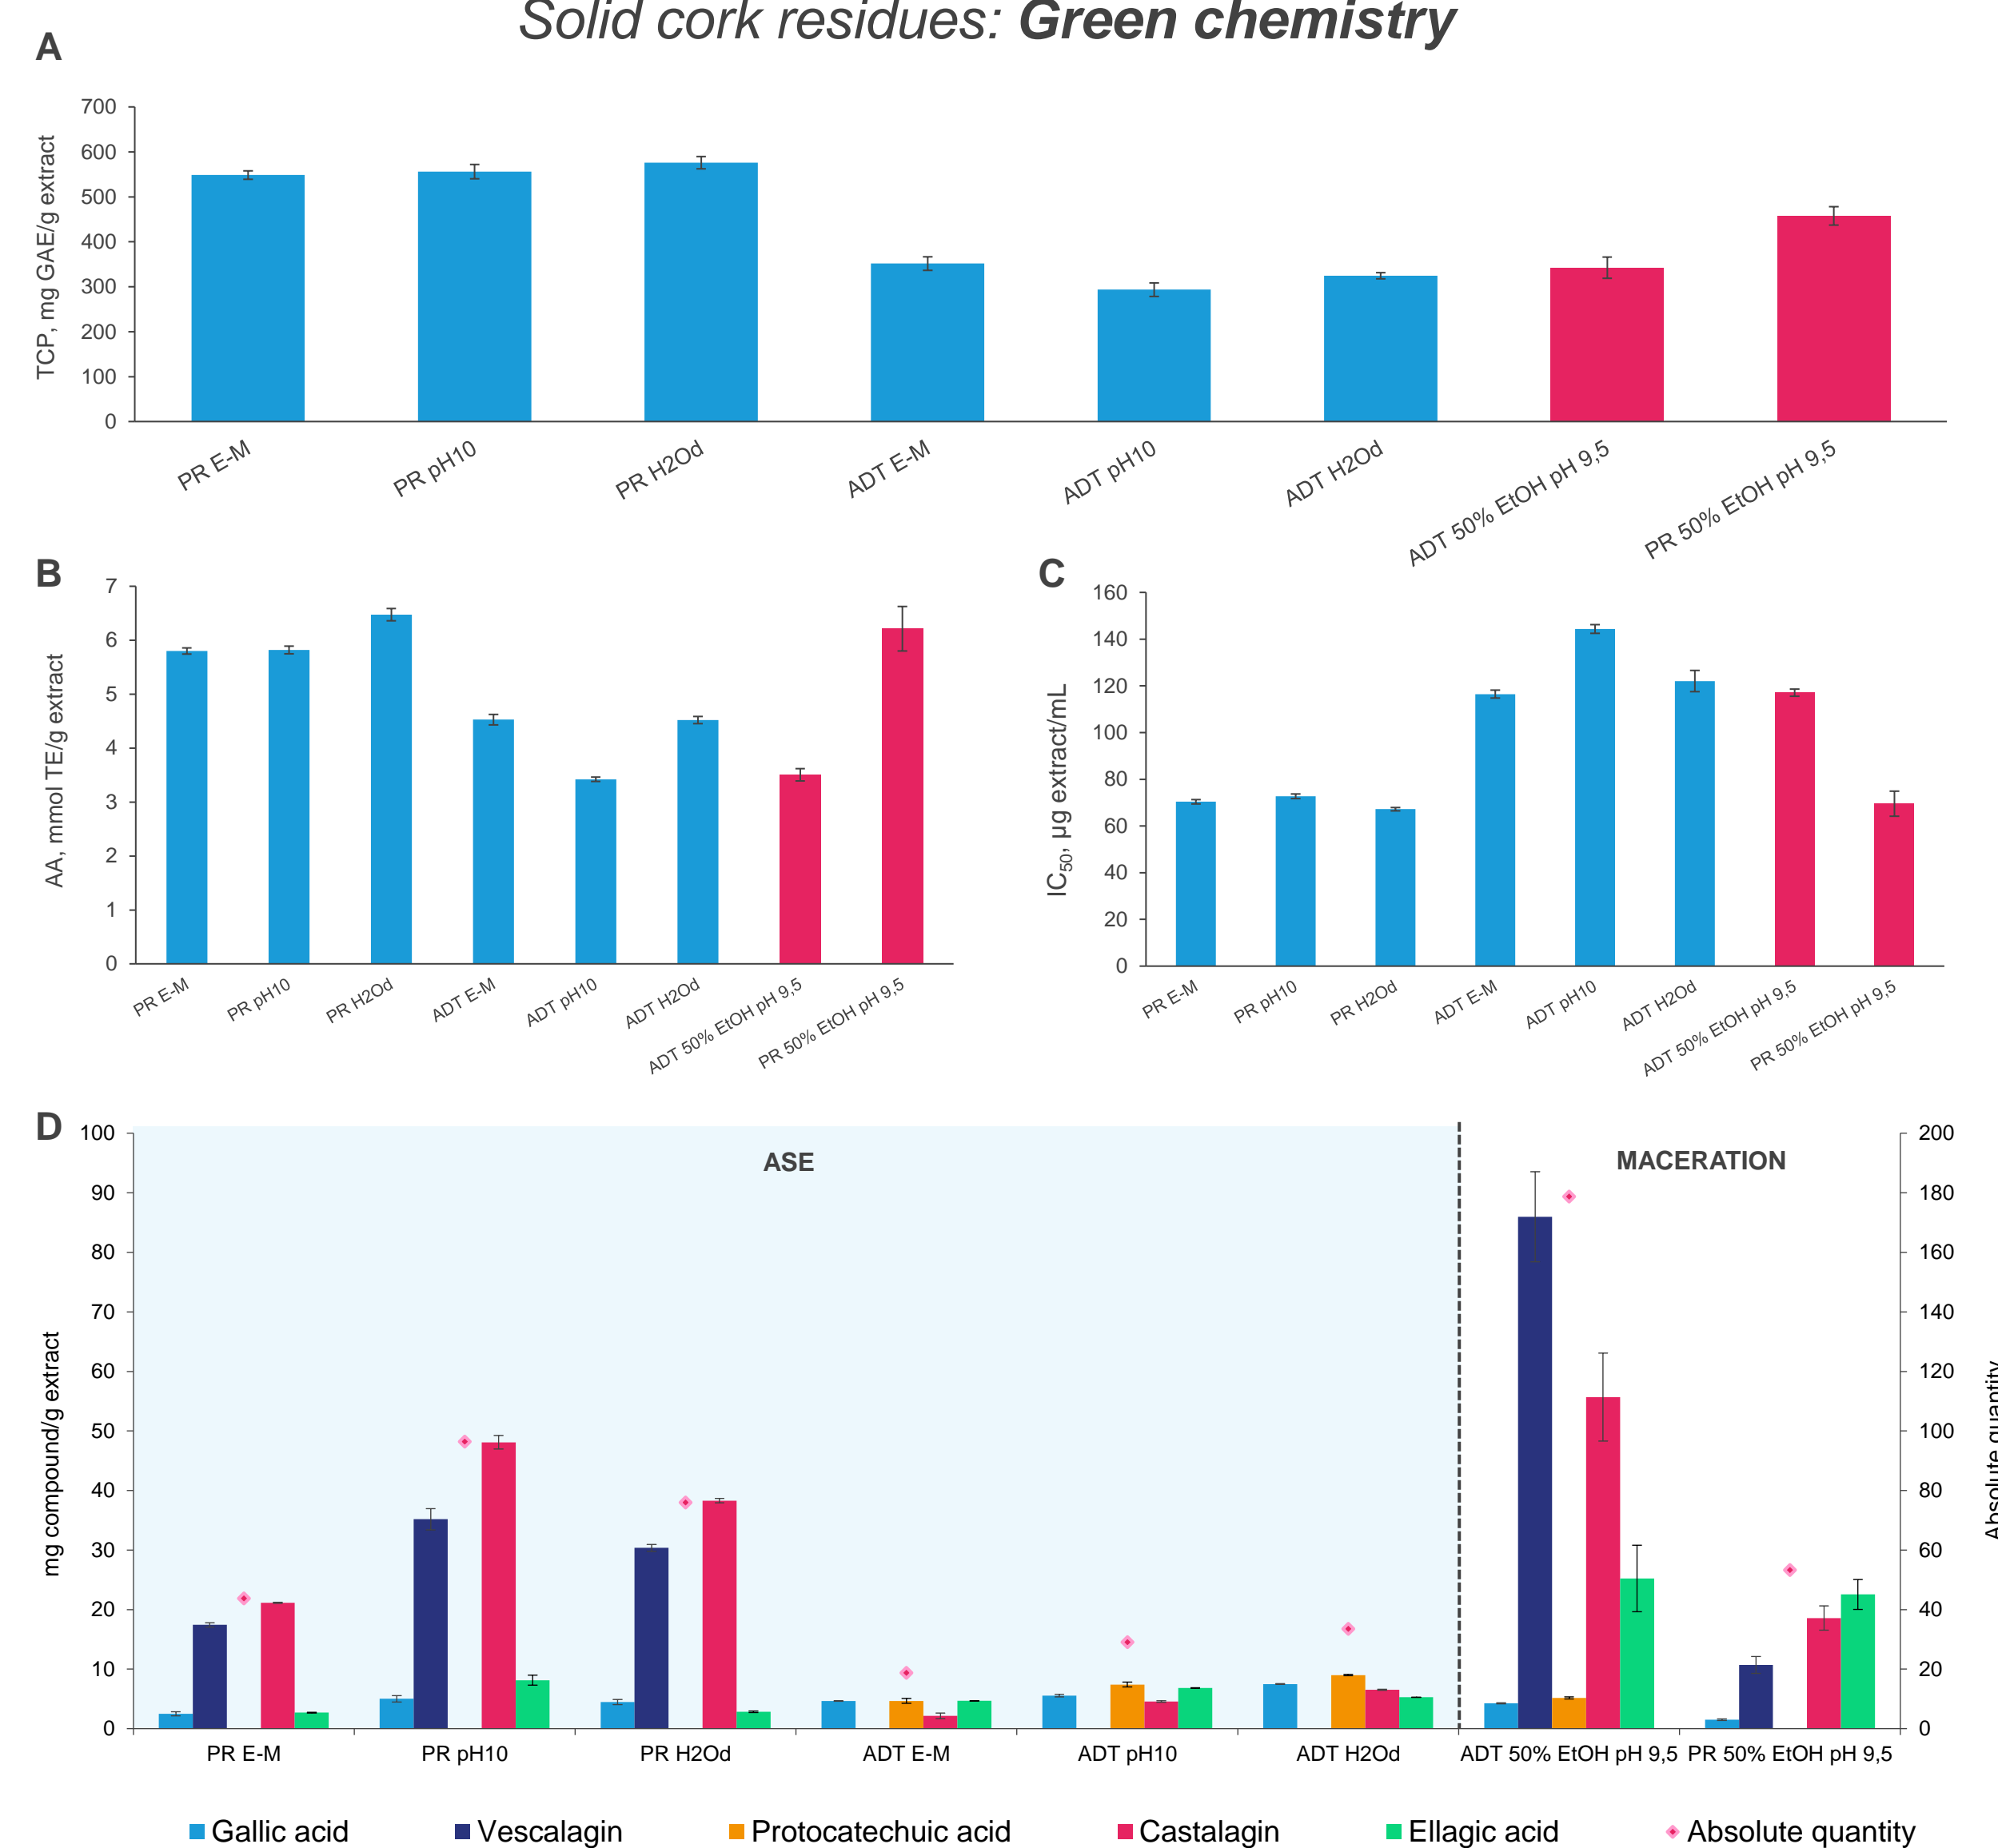


Figure 3. Characterization of extracts obtained by ASE (blue) and Maceration methods (pink).

A: Total phenol content; B: Antioxidant Activity; C: IC50; D: Low molecular weight phenolic compounds; Sample coding: PR (mill cork dust); ADT (high density granulated); E-M (ethanol 33%-methanol 0.38%); pH10 (water pH10); H2O (distilled water); pH9.5 (alkaline water pH9.5); 50% EtOH pH 9.5 (50% ethanol- alkaline water pH 9.5).

The results of these extraction processes are as following: extraction yields between 22-90mg extract/g dry cork, total phenolic content in the range 293-576mg GAE/g extract, antioxidant activity of 3.3-6.5mmol Trolox/g extract and IC50 between 67-144µg/ml.

Traditional extraction has allowed us to determine that two of the solid cork residues, ADT and PR, have the highest phenolic concentration. These two cork by-products have been used in the optimisation process based on green chemistry and led to the conclusion that the two most efficient extraction methods were maceration and ASE.